



Report No.: 25157-0
Order No.: AE25157
Client Reference: Check #4040
Date: June 9, 2008

DSET LABORATORIES

A Division of Atlas Material Testing Technology LLC
45601 North 47th Avenue
Phoenix, Arizona 85087-7042 USA
Phone (623) 465-7356
Toll Free (800) 255-3738
Fax (623) 465-9409
www.atlaswsg.com

**HEMISPHERICAL SPECTRAL REFLECTANCE
and
TOTAL EMITTANCE TEST REPORT**

prepared for:

TILE TECH PAVERS
1914 West Pico Blvd.
Los Angeles, CA 90006


presented by:

Atlas Weathering Services Group
DSET Laboratories
45601 North 47th Avenue
Phoenix, AZ 85087-7042
Phone: 623-465-7356
FAX: 623-465-9409

This test report contains only findings and results arrived at after employing the specific test procedures and standards listed herein. It does not constitute a recommendation for, endorsement of, or certification of the product or material tested. Atlas Weathering Services Group makes no warranty, expressed or implied, except that the test has been performed, and a report prepared, based upon the sample or samples furnished by the client. Extrapolation of data from the sample or samples relating to the batch or lot from which it was obtained may not correlate and should be interpreted accordingly with extreme caution. We assume no responsibility for variations in quality, composition, appearance, performance, or other feature of similar subject matter produced by persons or under conditions over which we have no control. This report shall not be reproduced except in full without the written approval by Atlas Weathering Services Group.


This report contains 5 pages

Prepared by:

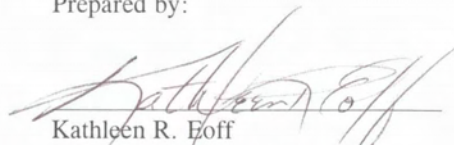

Kathleen R. Eoff
Senior Technician, Optics

Approved by:

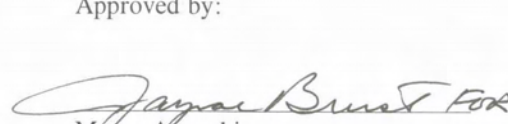

Marge Awarski
Group Leader, Evaluations Services

TEST INSTRUMENTS GROUP

- ATLAS MATERIAL TESTING TECHNOLOGY
- ATLAS MATERIAL TESTING TECHNOLOGY GmbH

WEATHERING SERVICES GROUP

- SOUTH FLORIDA TEST SERVICE
- DSET LABORATORIES



ISO/IEC 17025
CERT #717.01



TILE TECH PAVERS
Report No.: 25157-0
Order No.: AE25157
Client Reference: Check #4040
Date: June 9, 2008
Page 5 of 5

**HEMISPHERICAL SPECTRAL REFLECTANCE
and
TOTAL EMITTANCE TEST REPORT**

4.0 RESULTS

Reflectance and SRI:

Specimen Code	% Solar Reflectance	SRI
Penny Lane	73.4	91
White Black Shot	63.9	79
Gray Black	26.8	30
Charcoal	15.1	15
Natural	59.5	73
Vanilla Gray	47.8	57

Emittance:

Specimen Code	Reflectance (ρ) Measured	Near-Normal Emittance (ϵ) Calculated
Penny Lane	.05	.95
White Black Shot	.05	.95
Gray Black	.05	.95
Charcoal	.05	.95
Natural	.05	.95
Vanilla Gray	.05	.95

TEST INSTRUMENTS GROUP
■ ATLAS MATERIAL TESTING TECHNOLOGY
■ ATLAS MATERIAL TESTING TECHNOLOGY GmbH

WEATHERING SERVICES GROUP
■ SOUTH FLORIDA TEST SERVICE
■ DSET LABORATORIES



An **AMETEK** Company

DSET LABORATORIES

A Division of Atlas Material Testing Technology LLC
45601 North 47th Avenue
Phoenix, Arizona 85087 U.S.A.
Phone: +1 623-465-7356
Toll Free: 800-255-3738 (U.S. only)
Fax: +1 623-465-9409
www.atlas-mts.com

Report No.: 30643-0
Order No.: AE30643
Client Reference: Check #6231
Date: September 17, 2011

HEMISPHERICAL SPECTRAL REFLECTANCE
and
TOTAL EMITTANCE TEST REPORT

prepared for:

TILE TECH PAVERS
1914 West Pico Blvd.
Los Angeles, CA 90006


presented by:

Atlas Weathering Services Group
DSET Laboratories
45601 North 47th Avenue
Phoenix, AZ 85087-7042
Phone: 623-465-7356
FAX: 623-465-9409

This test report contains only findings and results arrived at after employing the specific test procedures and standards listed herein. It does not constitute a recommendation for, endorsement of, or certification of the product or material tested. Atlas Weathering Services Group makes no warranty, expressed or implied, except that the test has been performed, and a report prepared, based upon the sample or samples furnished by the client. Extrapolation of data from the sample or samples relating to the batch or lot from which it was obtained may not correlate and should be interpreted accordingly with extreme caution. We assume no responsibility for variations in quality, composition, appearance, performance, or other feature of similar subject matter produced by persons or under conditions over which we have no control. This report shall not be reproduced except in full without the written approval by Atlas Weathering Services Group.

This report contains 5 pages

Prepared by:



Kathleen R. Eoff
Senior Technician, Optics

Approved by:



Marge Awarski
Group Leader, Evaluation Services



